

Influence of Doping of Titanium Dioxide by Zirconium and Niobium on its Morphology

L.M. Humeniuk, I.M. Budzulyak, R.V. Ilnytskyk

Vasyl Stefanyk Precarpathian National University, 57, Shevchenka Str., 76000 Ivano-Frankivsk, Ukraine

(Received 16 October 2013; published online 31 January 2014)

Structure porosity and specific surface area of undoped and doped nanodispersed titanium dioxide with Zr, Nb was investigated. The porous structure of TiO_2 is caused by its intervals between nanoparticles and their agglomerates. Surface morphology of obtained materials was determined by isotherms of nitrogen adsorption-desorption. Specific surface area of nanodispersed titanium dioxide, according to the results, consists 182 m^2/g . It was found, that during doping of titanium dioxide with zirconium comparing to origin TiO_2 specific surface increases in 30 %, and for niobium-doped decreases in 20 %. Pore-size distribution for $\text{TiO}_2\langle\text{Nb}\rangle$ correspond to the value of 10-15 nm.

Keywords: Doping, Titanium dioxide, Specific surface.

PACS number: 68.47.Gh

1. INTRODUCTION

Titanium dioxide, especially nanosized TiO_2 , is a promising material in nowadays technologies [1]. TiO_2 obtaining in different polymorphs (anatase, rutile and brookite) and its modification is a quite topical at this time because it has large specific surface and structure which is capable for intercalation process. Modification of TiO_2 is mostly done by doping with admixture, which change both the crystal structure and its morphology [2]. This paper presents the study of the pore structure of origin titanium dioxide and its change caused by chemical admixture of transition metals Nb and Zr. We have found [3, 4], that modified in such a way TiO_2 has a number of advantages, including its larger surface area, smaller particles and better thermal stability [5-7], which is crucial fact for its use as an electrode material [8].

The porous structure of TiO_2 is caused by its granular structure and it is the intervals between primary and secondary (agglomerates) particles. SEM image of the surface material of TiO_2 , $\text{TiO}_2\langle\text{Zr}\rangle$, $\text{TiO}_2\langle\text{Nb}\rangle$ indicates on a slight increase of spherical grains for $\text{TiO}_2\langle\text{Nb}\rangle$ [3].

According to data [9], niobium-doping at concentration of 1 %, 3 %, 5 % causes to decrease of TiO_2 particles for anatase and their increase for rutile. Interacting with each other oxides TiO_2 and ZrO_2 form a solid solution $\text{ZrxTi}_{1-x}\text{O}_2$ with large surface area, high thermal stability and mechanical strength [10].

2. EXPERIMENTAL DETAILS

Surface morphology of doped titanium dioxide which main structure is anatase was determined by isotherms of nitrogen adsorption-desorption at a temperature $T = 77$ K on the device Quantachrome Autosorb (Nova 2200e). Calculation of the specific area and determination of the pore distribution were carried out automatically using computer programs.

Samples were degased in a vacuum chamber with a residual pressure of ~ 1.3 Pa at 373 K for 17 hours. The total pore volume was calculated by volume of adsorbed nitrogen according to desorption isotherm. The method of BJH (Barrett-Joyner-Halendy) was used to determine the porosity. The specific surface area was determined by multipoint method.

3. RESULTS AND DISCUSSION

Obtained titanium dioxide by sol-gel technology is nano dispersed with an average particle size of 10 nm. Zirconium and niobium concentration in TiO_2 was 20 mol % in molar mass, but impurity phases were not observed on X-ray diffractograms [3, 4], indicating its complete solubility in the structure of the main material.

Fig. 1 shows the adsorption-desorption isotherms of nitrogen (a) and pore-size distributions (b) defined by BJH method for the origin TiO_2 . Isotherm (Fig. 1a) is characterized by two hysteresis loops at relative pressures $0.4 < P/P_0 < 0.6$ and at $0.05 < P/P_0 < 0.1$.

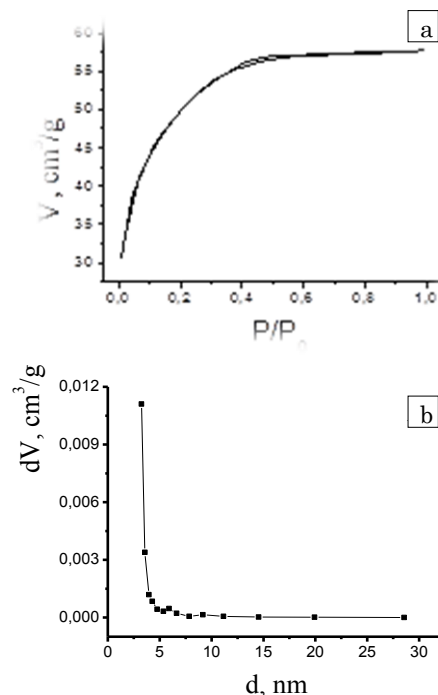


Fig. 1 – N_2 isotherms (a) and pore-size distribution (b) for origin TiO_2

This is a Type I isotherm according to the IUPAC classification, which is inherent for microporous substances and describes the material as a matter of uniform surface, which is consistent with the SEM image, where by the surface of TiO_2 consists of uniform spherical nanoparticles.

Maximum pore-size distribution for TiO₂ (Fig. 1b) corresponds to the value of 3 nm. According to the definition of pore size classification this value for TiO₂ corresponds to micropores as consistent with the obtained isotherm on Fig. 1a.

For niobium-doped titanium dioxide nitrogen isotherm is Type V, which is typical for micro- and mesoporous materials and indicates a significant pore increase after doping.

One explanation for this phenomenon is the increase of nanoparticles surface area or their agglomeration and thus increases of the relative part of the pores with larger size. The value of pore-size distribution for TiO₂(Nb) is presented in Fig. 2b.

Comparing with the preceding distribution pore-size distribution in the 10-15 nm region is observed, which corresponds to mesopores, although there are micropores too.

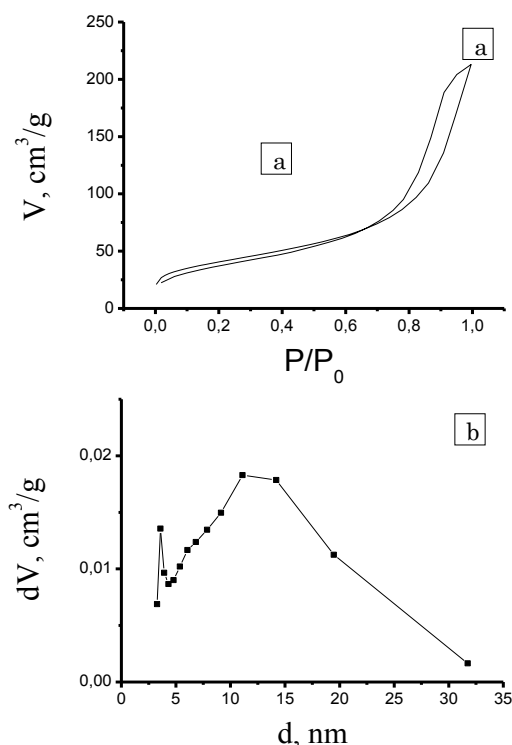


Fig. 2 – N₂ isotherms (a) and pore-size distribution for TiO₂ doped with Nb (b)

For zirconium-doped titanium dioxide (Fig. 3) isotherm indicates an increase in the porosity of the material compared to the origin TiO₂ and Nb-doped TiO₂. For this case it is a type III isotherm, which is close to the V type. Hysteresis loop (Fig. 3a) the same as for previous material at pressures of $0.8 < P/P_0 < 0.98$ corresponds to filling with nitrogen of major structural pores and mesopores between gaps of agglomerated (secondary) particles. According to Fig. 3b it is clear that the maximum of distribution is for the micropores with the size of 3 nm as to the origin TiO₂.

Thus, doping changes the morphology of titanium dioxide, increasing the pore size, especially for the case of TiO₂(Nb). Table 1 shows the parameters of TiO₂ porous structure.

Especially it is very important that compared with the origin titanium dioxide and TiO₂(Nb) specific surface determined by the method of BET and t-method TiO₂(Zr) is the largest and corresponds to Fig. 3b.

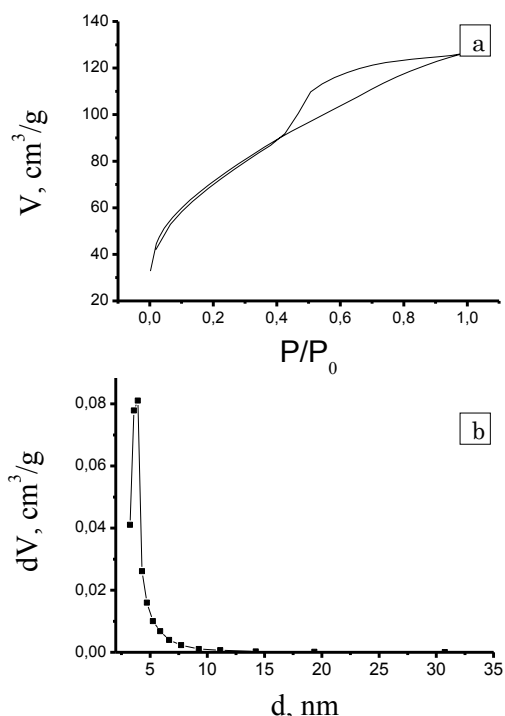


Fig. 3 – N₂ isotherms of nitrogen (a) and pore size distribution for Zr-doped TiO₂ (b)

Table 1 – Characterization of surface and pore structure of nano dispersed TiO₂

	TiO ₂	TiO ₂ (Nb)	TiO ₂ (Zr)
Specific surface area (BET), m ² /g	182	145	258
Specific surface area (t-method), m ² /g	132	27,5	67
Specific pore volume, cm ³ /g	0,09	0,33	0,18
Specific pore volume (t-method), cm ³ /g	0,057	0,012	0,029
Average pore size, nm	2	9	3

4. CONCLUSIONS

Pore size and specific surface area of nanodispersed origin, zirconium-and niobium-doped titanium dioxide have been calculated by BJH and BET methods.

It was found that during zirconium-doping specific

surface area increases significantly to 258 m²/g relatively to the value for the origin TiO₂ and decreases to 145 m²/g for niobium-doped TiO₂. Micropores are predominant, especially for TiO₂ and TiO₂(Zr). For TiO₂(Nb) maximum pore size distribution is 10-15 nm.

Вплив легування діоксиду титану ніобієм і цирконієм на морфологію поверхні

Л.М. Гуменюк, І.М. Будзуляк, Р.В. Ільницький

Прикарпатський національний університет ім. В. Стефаника, вул. Шевченка, 57, 76000 м. Івано-Франківськ, Україна

Досліджено пористу структуру та питому площу поверхні нанодисперсного діоксиду титану нелегованого та легovanого Zr і Nb. Встановлено, що пористість нанодисперсного TiO₂ являє собою порожнини між наночастинками та їх агломератами. Шляхом аналізу ізотерм адсорбції-десорбції азоту визначалася морфологія поверхні матеріалів. Питома площа поверхні нелегованого діоксиду титану TiO₂ (розмір частинок ~ 10 нм), становила 182 м²/г. Показано, що при легуванні діоксиду титану, цирконієм в порівнянні із нелегованим TiO₂ площа питомої поверхні збільшується на 30 %, а у випадку легування ніобієм зменшується на 20 %. Основна частина пор діоксиду титану легovanого ніобієм володіє розміром 10-15 нм.

Ключові слова: Легування, Діоксид титану, Питома площа поверхні.

Влияние легирования диоксида титана ниобием и цирконием на морфологию поверхности

Л.М. Гуменюк, И.М. Будзуляк, Р.В. Ильницкий

Прикарпатский национальный университет им. В. Стефаника, ул. Шевченка, 57, 76000 г. Ивано-Франковск, Украина

Исследованы пористая структура и удельная площадь поверхности нанодисперсного диоксида титана нелегированного и легированного Zr и Nb. Установлено, что пористость нанодисперсного TiO₂ представляет собой интервалы между наночастицами и их агломератами. Морфология поверхности материалов определялась путем анализа изотерм адсорбции-десорбции. Удельная площадь поверхности нелегированного диоксида титана TiO₂ (размер частиц ~ 10 нм), согласно полученным результатам, составила 182 м²/г. Показано, что при легировании диоксида титана, цирконием по сравнению с нелегированным TiO₂ площадь удельной поверхности увеличивается на 30 %, а в случае легирования ниобием – уменьшается на 20 %. Основная часть пор для диоксида титана легированного ниобием характеризуется размером 10-15 нм.

Ключевые слова: Легирование, Диоксид титана, Удельная площадь поверхности.

REFERENCES

1. I.F. Mironyuk, V.O. Kotsyubynskyy, B.K. Ostafiychuk, *Synthesis, structure and electrochemical properties of oxide nanomaterials: a monograph* (Ivano-Frankivsk: Vasyl Stefanyk Precarpathian National University: 2011).
2. A. Zaleska, *Recent patents of engineering* 2, 57 (2008).
3. L.M. Humeniuk, I.I. Grigorchak, I.M. Budzulyak, R.V. Ilnytsky, *Phys. Chem. Solids* 13, 685 (2012).
4. I.M. Budzulyak, L.M. Humeniuk, R.V. Ilnytsky, P.I. Yaremy, *Visnuk of the Precarpathian University. Chemistry* 2, 94 (2012).
5. E. Sotter, X. Vilanova, E. Llobet, M. Stankova, X. Correig, *J. Optoelectron. Adv. M.* 7, 1395 (2005).
6. M.V. Koudriachova, N.M. Harrison, *J. Mater. Chem.* 16, 1973 (2006).
7. N. Tsvetkov, L. Larina, O. Syevaleevskiy, *Energy Environ. Sci.* 4, 1480 (2011).
8. A.L. Rahima, The University of Western Ontario London, Ontario, Canada, 265 (2008).
9. P. Sukon, L. Chaikarn, W. Khatcharin, *Sensors* 11, 472 (2011).
10. M.R. Benjaram, K. Ataulah, *Cataly. Rev.* 47, 257 (2005).